

Contents lists available at [ScienceDirect](https://www.sciencedirect.com)

# Progress in Materials Science

journal homepage: [www.elsevier.com/locate/pmatsci](http://www.elsevier.com/locate/pmatsci)

## From simple binary to complex multicomponent eutectic alloys

Isaac Chang<sup>\*</sup>, Qing Cai

Brunel Centre for Advanced Solidification Technology (BCAST), Brunel University London, Kingston Lane, Uxbridge UB8 3PH, UK

### ARTICLE INFO

#### Keywords:

Eutectic  
Multicomponent alloys  
Microstructure  
Differential scanning calorimetry  
Hardness

### ABSTRACT

The eutectic solidification of almost all binary and majority of key ternary alloy systems have been studied and modelled extensively. The development of eutectic microstructure in ternary, multicomponent and high entropy alloys have generated potential engineering alloys with superior mechanical/magnetic properties that outperform their traditional binary eutectic counterparts due to refined microstructure and/or the presence of dual hard/soft phase mixture. Currently, our understanding of the eutectic solidification is mainly restricted to alloy systems having upto 3 constituents (eg. ternary eutectic). There exists a knowledge gap in our understanding of the solidification behaviour of high order multicomponent eutectic alloys. This review article gives a brief background of the development of eutectic alloys from binary to senary multicomponent systems, together with an overview of recent development of complex microstructures of aluminium based multicomponent alloys with five or more constituents at/near eutectic compositions. Although the number of crystalline phases coexisted in the Al-based eutectic alloys increases with increasing number of constituents. The solidification of a melt at near eutectic composition of 13-element alloy system has led to the development of seven crystalline phases with predominantly non-cooperative growth, leading to a microstructure free of lamellar feature, as compared to their low-order constituent alloy counterparts. Finally, the hardness of Al-based eutectic alloy increases significantly as the number of constituents in excess of ten. This opens up a new opportunity to develop ultrahigh strength alloys based on high-order multicomponent eutectic alloy systems.

### 1. Introduction

Eutectic alloys refer to a unique class of material system comprised of more than one constituent and they exhibit the lowest temperature of melting/freezing as compared to the melting point of any of the constituents. The word eutectic is derived from the Greek word “eutektos” which implies easily melted and it was first used by Guthrie [1] in 1884. Eutectic systems are found everywhere in nature, and have been reported in a wide range of materials including organic [2,3], ceramic [4], metallic [1,5] and semi-metallic [6,7] alloys. They possess a unique composite microstructure of multiple phases, combined with outstanding mechanical and electrical/magnetic properties that exceed their elemental or solid solution counterparts. Our understanding of eutectic materials in terms of their solidification behaviour, crystallographic relationship between eutectic phases and their properties have been generated through a combination of theoretic and experimental studies for over 130 years. Earlier eutectic alloys were based on low melting point elements [1] including Sn, Pb, Bi, Zn, Cd. Later, they have been developed primarily to use in joining applications such as soldering or brazing industries due to its low melting point. Most aluminium-based casting alloys are developed based on eutectic systems for better

<sup>\*</sup> Corresponding author.

E-mail address: [Isaac.chang@brunel.ac.uk](mailto:Isaac.chang@brunel.ac.uk) (I. Chang).

<https://doi.org/10.1016/j.pmatsci.2021.100779>

Received 7 August 2020; Received in revised form 13 December 2020; Accepted 11 February 2021

Available online 27 February 2021

0079-6425/© 2021 The Authors.

Published by Elsevier Ltd.

This is an open access article under the CC BY license

(<http://creativecommons.org/licenses/by/4.0/>).

**Table 1**

A selected range of studied eutectic alloys from low to high order constituent systems.

Alloy	Phases	References
<b>Binary</b>		
Al <sub>84</sub> Cu <sub>16</sub>	α-Al + Al <sub>2</sub> Cu	[9,10]
Al <sub>61</sub> Ag <sub>39</sub>	α-Al +	[11]
Al <sub>96.9</sub> Ni <sub>3.1</sub>	α-Al + Al <sub>3</sub> Ni	[9]
Co <sub>90.5</sub> Zr <sub>9.5</sub>	HCP Co + Co <sub>11</sub> Zr <sub>2</sub>	[12]
Fe <sub>83</sub> B <sub>17</sub> (annealed)	α-Fe + Fe <sub>2</sub> B	[13]
Fe <sub>90.2</sub> Zr <sub>9.8</sub>	BCC Fe + Fe <sub>23</sub> Zr <sub>6</sub>	[12]
Fe <sub>90</sub> Nb <sub>10</sub>	α-Fe + Fe <sub>2</sub> Nb	[14]
Ni <sub>80</sub> Si <sub>20</sub>	δ-Ni <sub>2</sub> Si + γ-Ni <sub>31</sub> Si <sub>12</sub>	[15]
Ni <sub>55</sub> Si <sub>45</sub>	γ-Ni <sub>31</sub> Si <sub>12</sub> + NiSi	[15]
Ni <sub>70</sub> Si <sub>30</sub>	δ-Ni <sub>2</sub> Si + γ-Ni <sub>31</sub> Si <sub>12</sub>	[15]
Ni <sub>45</sub> Si <sub>55</sub>	α-NiSi <sub>2</sub> + NiSi	[15]
Ti <sub>70.5</sub> Fe <sub>29.5</sub>	β-Ti + TiFe	[16]
<b>Ternary</b>		
Al <sub>76.07</sub> Cu <sub>13.6</sub> Ag <sub>10.27</sub>	α-Al + θ-Al <sub>2</sub> Cu + δ-AlAg <sub>2</sub>	[43]
Al <sub>64.6</sub> Mg <sub>34.6</sub> Ni <sub>0.8</sub>	α-Al + NiAl <sub>3</sub> + Mg <sub>2</sub> Al <sub>3</sub>	[44]
Al <sub>81</sub> Cu <sub>13</sub> Si <sub>6</sub>	α-Al + θ-Al <sub>2</sub> Cu + Si	[19,41,42]
Co <sub>49.2</sub> Fe <sub>49.2</sub> Zr <sub>9.6</sub>	BCC Co(Fe) + Co(Fe <sub>23</sub> Zr <sub>6</sub> )	[12]
Fe <sub>83</sub> B <sub>16</sub> Si <sub>1</sub>	α-Fe(Si) + Fe <sub>3</sub> B + Fe <sub>2</sub> B	[49]
Fe <sub>83</sub> B <sub>16</sub> Cu <sub>1</sub>	α-Fe(Cu) + Fe <sub>3</sub> B + Fe <sub>2</sub> B	[49]
Fe <sub>75</sub> Si <sub>15</sub> Ti <sub>10</sub>	α-Fe(Si) + (Fe,Si) <sub>2</sub> Ti	[23]
Fe <sub>87</sub> Ti <sub>7</sub> Zr <sub>6</sub>	α-Fe + Fe <sub>2</sub> Ti	[24]
Ti <sub>67.79</sub> Fe <sub>28.36</sub> Sn <sub>3.85</sub>	β-Ti + FeTi	[21,22]
<b>Quaternary</b>		
Al <sub>77</sub> Cu <sub>12</sub> Si <sub>7</sub> Mg <sub>3</sub>	α-Al + θ-Al <sub>2</sub> Cu + Si + Q(Al <sub>4</sub> Cu <sub>2</sub> Mg <sub>8</sub> Si <sub>7</sub> )	[50]
CoCrFeNi <sub>2.1</sub>	FCC + B2	[28]
Fe <sub>71</sub> Si <sub>15</sub> Ti <sub>10</sub> Cu <sub>4</sub>	α-Fe(Si) + (Fe,Si) <sub>2</sub> Ti	[23]
Fe <sub>81</sub> Ti <sub>7</sub> Zr <sub>6</sub> B <sub>6</sub>	α-Fe + Fe <sub>2</sub> Ti	[24]
Nb <sub>25</sub> Sc <sub>25</sub> Ti <sub>25</sub> Zr <sub>25</sub>	HCP + BCC	[29]
CrFeNi <sub>2</sub> Al <sub>0.8</sub>	FCC + B2/BCC	[30]
<b>Quinary</b>		
AlCrFeNiMo <sub>0.2</sub>	FeCr type solid solution + AlNi intermetallic compound	[31]
AlCoCrFeNi <sub>3</sub>	B2 + FCC (L1 <sub>2</sub> )	[27]
AlCo <sub>2</sub> CrFeNi <sub>2</sub>	B2 + FCC (L1 <sub>2</sub> )	[27]
Fe <sub>28.2</sub> Ni <sub>18.8</sub> Mn <sub>32.9</sub> Al <sub>14.1</sub> Cr <sub>6</sub>	FeMn + NiAl	[38]
CoCrFeNiMo <sub>0.8</sub>	FCC + Cr <sub>3</sub> Mo <sub>21</sub> Ni <sub>20</sub>	[32]
CoFeNi <sub>1.4</sub> VMo	FCC + Co <sub>2</sub> Mo <sub>3</sub>	[33]
CoFeNi <sub>2</sub> V <sub>0.5</sub> Nb <sub>0.75</sub>	FCC + Fe <sub>2</sub> Nb type Laves	[34]
CoCrFeNiZr <sub>0.45</sub>	γ-Fe FCC + ZrCo <sub>2</sub> type Laves	[35]
Co <sub>2</sub> Mo <sub>0.6</sub> Ni <sub>2</sub> VW <sub>0.8</sub>	FCC + Co <sub>7</sub> Mo <sub>6</sub> -type μ phase	[36]
Hf <sub>0.55</sub> CoCrFeNi <sub>2</sub>	FCC + Ni <sub>7</sub> Hf <sub>2</sub>	[37]
Ta <sub>0.65</sub> CoCrFeNi <sub>2</sub>	FCC + (Co,Ni) <sub>2</sub> Ta	[37]
Zr <sub>0.6</sub> CoCrFeNi <sub>2</sub>	FCC + Ni <sub>7</sub> Zr <sub>2</sub>	[37]
<b>Senary</b>		
CoCrFeNiMnPd	CoCrFeNi + Mn <sub>7</sub> Pd <sub>9</sub>	[39]
AlCoCrFeNiNb <sub>0.6</sub>	(CoCr)Nb + BCC	[40]

castability to enable the manufacturing of engineering components for light-weighting design. Eutectic alloys offer desirable mechanical and magnetic properties for potential exploitation in structural and soft magnetic applications. Recently, eutectic alloys have been exploited as phase change material for latent heat thermal energy storage [8]. Finally, the emerging development of eutectic microstructure in equiatomic/near equiatomic multicomponent systems known as high entropy alloys (HEAs) has opened up the increasing research interest on eutectic alloys in high-order multicomponent systems, which provides an excellent opportunity to discover new materials with new properties.

## 2. Previous and current research of eutectic alloys

Eutectic solidification of binary alloys [9–16] involves the nucleation and growth of a two-phase mixture. The morphology of such regular two-phase eutectic microstructure (e.g. lamellar, rod-like, fibrous etc.) depends on materials characteristics such as faceted/non-faceted nature, entropy of fusion and proportion of each solid phase, as well as the solidification conditions [17,18]. Such two-phase eutectic microstructure is not limited to binary alloy systems but are also found in ternary (e.g. Al-Si-Cu [19], Ag-Cu-Ge [20], Ti-Sn-Fe [21,22], Co-Fe-Zr [12], Fe-Si-Ti [23], Fe-Ti-Zr<sup>24</sup>) and other quaternary [25–30], quinary [27–38] and senary [39,40] multicomponent alloy systems. However, other multiphase eutectic microstructure beyond two-phase mixture have been observed in ternary (e.g. Al-Cu-Si [19,41,42], Al-Cu-Ag [42,43], Al-Ni-Mg [44], Nb-Al-Ni [45,46], Al-Cu-Ni [47], Fe-Mo-Si [48], Fe-B-Cu [49]) and quaternary (e.g. Al-Cu-Si-Mg [50]) eutectic alloys. There are hundreds or more eutectic/near eutectic alloys [18] found in metallic systems comprising of upto 6 constituents. Table 1 gives a selected list of these eutectic alloys from binary to senary systems. It is

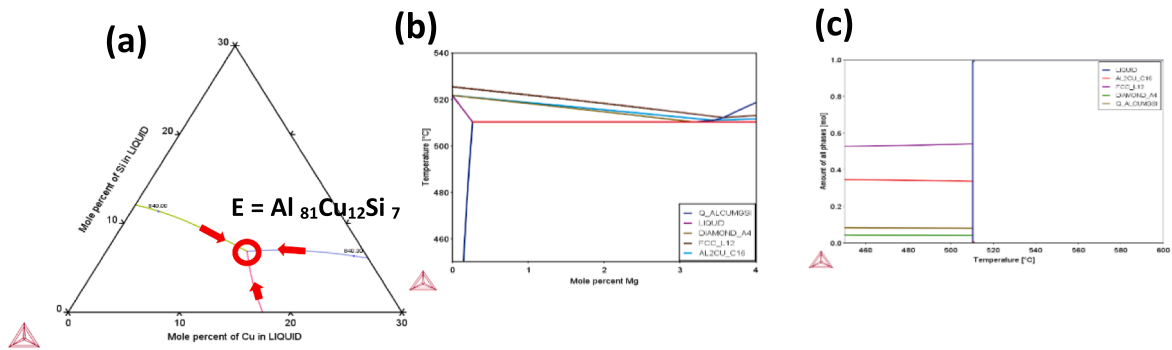


Fig. 1. Thermocal prediction of Al-Cu-Si equilibrium phase diagram (a), vertical section from ternary  $Al_{81}Cu_{12}Si_7$  with increasing Mg content (b) and fraction of solid phases as a function of temperature at predicted quaternary  $Al_{77}Cu_{12}Si_7Mg_3$  eutectic composition (c).

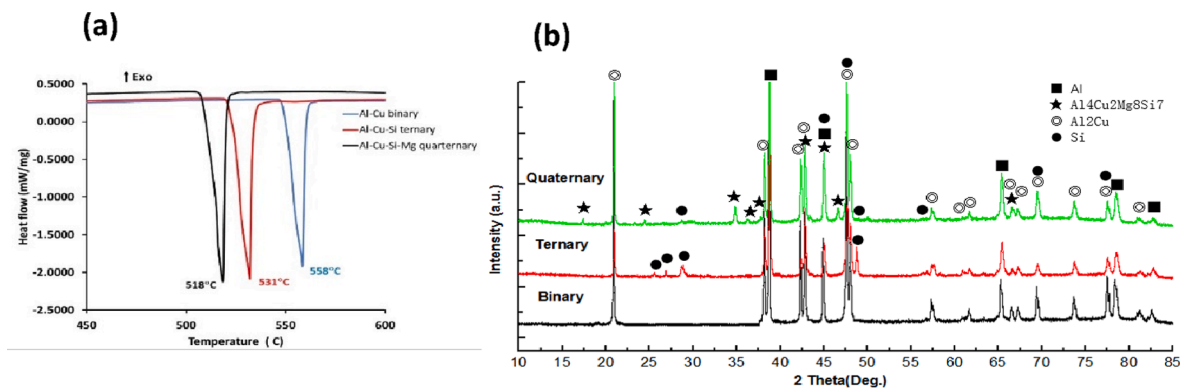


Fig. 2. DSC traces (a) and XRD spectra (b) of suction cast  $Al_{84}Cu_{16}$ (binary),  $Al_{81}Cu_{12}Si_7$ (ternary) and  $Al_{76}Cu_{14}Si_7Mg_3$ (quaternary) alloys.

interesting to see that the total number of co-existed phases present in the eutectic microstructure is below four even for the senary alloys.

### 3. Search for eutectic composition.

Not all binary alloys can form eutectic alloys. This is because the valence electrons of the constituents are not always compatible with the formation of joint crystal lattice. However, these binary eutectic alloys are frequently formed at near simple composition ratio [51] of their constituents, such as 8/1, 5/1, 3/1, 2/1 and 3/2 [52]. This was explained previously by the short-range atomic ordering of the eutectic liquid structure into specific arrangements of icosahedral clusters [52,53]. Recently, a new structural tool based on the cluster-plus-glue-atom model [54] was used to derive the composition formulas of binary eutectics. The eutectic compositions and temperatures of many binary and ternary alloys can be extracted from experimentally determined equilibrium phase diagrams listed in handbooks [55,56].

If all the eutectic phases formed are known beforehand, the eutectic composition and eutectic temperature,  $T_E$ , can be predicted using the following Schroeder-van Laar equation [57–59]:

$$\ln X_i = \frac{\Delta H_{fusion}^i}{R} \left( \frac{1}{T_E} - \frac{1}{T_i} \right)$$

where  $X_i$  is the molar fraction of the  $i^{\text{th}}$  phase,  $T_E$  is the eutectic temperature of the alloy and  $T_i$  is the melting temperature of the  $i^{\text{th}}$  phase. This approach has been applied to 16 binary (e.g. Al-Ga, Al-Ge-Al-Zn, Au-Ge, Pb-Sb etc.) and 6 ternary (e.g. Al-Ge-Sn, Cd-Pb-Sn etc.) eutectic alloys [60]. In general, the theoretic prediction agrees well with the general trends of eutectic temperature and compositions studied over a wide range of alloy systems. However, there are discrepancies between the predicted and the experimental data, which may be due to the assumption of ideal mixing in the Schroeder-van Laar equation. For quaternary alloys, the eutectic points can be determined by two-dimensional sections set construction [61] (tie-lines method) on the model of T-x-y-z and the intersection of the four surfaces of primary crystallization of the components based on data from binary and ternary alloy systems [58]. However, they rely on prior knowledge of all co-existed eutectic phases.

An alternative way to search the eutectic point, is to use the CALPHAD (CALculation of PHase Diagrams) software (e.g.

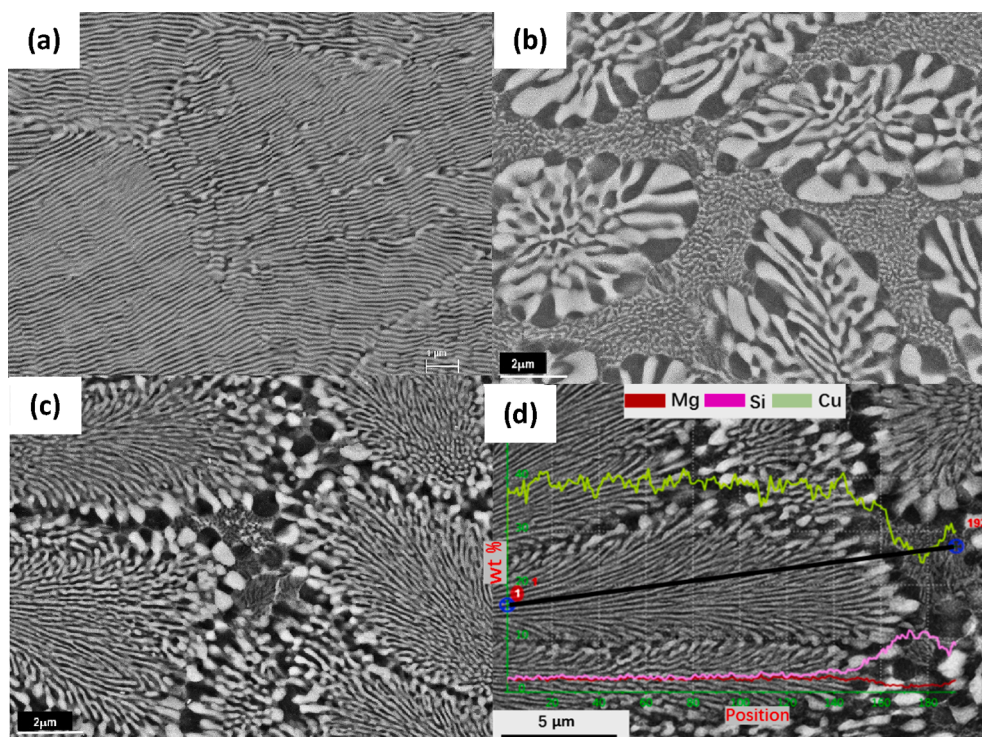


Fig. 3. SEM micrographs of suction cast  $\text{Al}_{84}\text{Cu}_{16}$  (a),  $\text{Al}_{81}\text{Cu}_{12}\text{Si}_7$  (b) and  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$  (c-d) alloys.

Thermocalc, Pandat, JMatPro, FactSage) [62], which is based on several geometric methods or mathematical formalisms to generate the phase diagrams. These programs use the properties of the individual components, single points of experimental data of mixtures and high order thermodynamic database [63] by extrapolation from the lower order constituent binary and ternary systems. For quinary alloys, the phase diagrams can be computed by fixing four elements first and then adjusting the 5th element [64–67]. There is a still huge challenge to design/locate the eutectic compositions in high-order constituent alloy systems without prior knowledge of eutectic phases.

In our studies, the initial prediction of the eutectic composition of Al-Cu-Si-Mg quaternary alloy was determined using Thermocalc software to achieve the lowest melting point for the solidification of a four-phase microstructure by adding Mg, together with the adjustment of Cu and Si contents of known ternary Al-Cu-Si ternary eutectic composition, as shown in Fig. 1. The predicted eutectic composition of Al-Cu-Si-Mg was found to be Al-12at%Cu-7at%Si-3at%Mg. This is similar to the reported Al-14at%Cu-7at%Si-3at%Mg [50] eutectic composition.

#### 4. From binary Al-Cu to quaternary Al-Cu-Si-Mg systems

Fig. 2a shows DSC curves of suction cast  $\text{Al}_{84}\text{Cu}_{16}$ (binary),  $\text{Al}_{81}\text{Cu}_{12}\text{Si}_7$ (ternary) and  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$ (quaternary) eutectic alloys subjected to a 20 K/min cooling cycle. They consisted of a single exothermic DSC peak, corresponding to eutectic solidification. The eutectic solidification peak occurs at 558 °C in  $\text{Al}_{84}\text{Cu}_{16}$  and decreases to 518 °C in  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$ . The heats of fusion (i.e. area under the peak) of ternary and quaternary eutectic alloys are found to be 448 J/g and 398 J/g, respectively. This corresponds to the decreasing eutectic temperature with increasing number of elements in the alloy system. The direct proportional relationship between melting temperature and heat of fusion has been reported in Al-Cu binary alloy [68]. Fig. 2b shows XRD spectra of suction cast  $\text{Al}_{84}\text{Cu}_{16}$ ,  $\text{Al}_{81}\text{Cu}_{12}\text{Si}_7$  and  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$  alloys. The number of eutectic phases increased from two (e.g.  $\alpha\text{-Al}$  and  $\theta\text{-Al}_2\text{Cu}$ ) in binary to four (e.g.  $\alpha\text{-Al}$ ,  $\theta\text{-Al}_2\text{Cu}$ , Si,  $\text{Q}(\text{Al}_4\text{Cu}_2\text{Mg}_8\text{Si}_7)$ ) in the quaternary alloys.  $\alpha\text{-Al}$  and  $\theta\text{-Al}_2\text{Cu}$  are two predominant eutectic phases present in all three alloys.

The as-cast microstructures of  $\text{Al}_{84}\text{Cu}_{16}$ ,  $\text{Al}_{81}\text{Cu}_{12}\text{Si}_7$  and  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$  alloys consisted of a lamellar eutectic microstructure, as shown in Fig. 3a–d. The average interlamellar spacing reduced from  $81.5 \pm 8$  nm in  $\text{Al}_{84}\text{Cu}_{16}$  to  $48.5 \pm 4$  nm in  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$ . However, both  $\text{Al}_{81}\text{Cu}_{12}\text{Si}_7$  and  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$  alloys comprised of cellular eutectic colonies separated by an intercellular region of nanometre-sized anomalous eutectic mixture free from any lamellar morphology. This suggests a decoupled growth of eutectic phases towards the end of the solidification process in ternary and quaternary eutectic alloys. The solute concentration varied from the centre of the cellular colony to the intercellular region. The intercellular region was found to be enriched in Si and deficient in Cu, as shown in Fig. 2d as a result of solute redistribution during the solidification process. Similar Si enrichment in the intercellular region has also been reported in Al-Cu-Si ternary eutectic alloy [41]. The formation of cellular eutectic and anomalous eutectic regions in ternary and

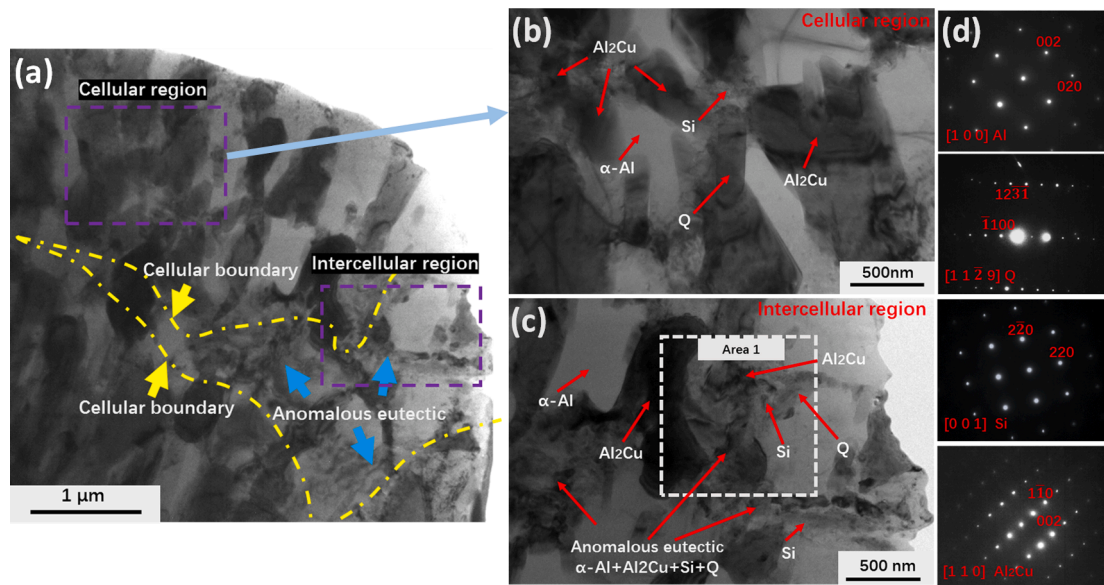


Fig. 4. TEM bright-field micrographs of  $Al_{76}Cu_{14}Si_7Mg_3$ : (a) cellular and intercellular regions; (b) cellular eutectic region with corresponding (c) intercellular region and (d) SADPs of eutectic phases.

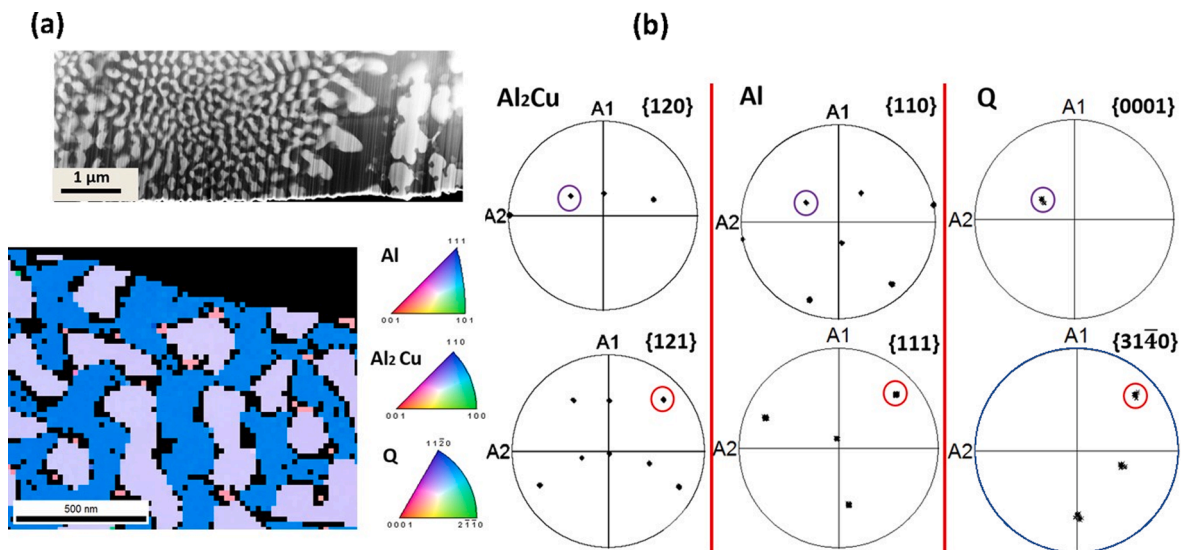



Fig. 5. T-EBSD and inverse pole figure map of suction cast  $Al_{76}Cu_{14}Si_7Mg_3$  (a) and identification of the orientation relationship between eutectic  $\alpha$ -Al,  $\theta$ - $Al_2Cu$  and Q phases present in the centre of cellular region (b).

quaternary alloys is due to uncontrolled growth conditions associated with relatively high cooling rate ( $10^2$ – $10^3$  K/s) [69] from suction casting process and the redistribution of additional atomic species such as Si, Mg. This can destabilise the solid/liquid interface (morphological instability) and encourage non-cooperative eutectic growth to yield cellular and anomalous eutectic regions, respectively. The coarse regions at the cellular boundaries, is resulted from the volume fraction adjustment [45] between constituent phases due to multiple solute rejection from the solidifying eutectic. The refinement of the interlamellar spacing in quaternary eutectic alloy can be attributed to (1) slow atomic mobility and growth rate associated with low eutectic temperature and (2) increasing resistance to the formation of appropriate crystalline phases to maintain cooperative eutectic growth by the presence of many different atomic species in the melt.


The four-phase microstructure of cellular eutectic colonies in  $Al_{76}Cu_{14}Si_7Mg_3$  alloy consisted of  $\alpha$ -Al and  $\theta$ - $Al_2Cu$  lamellae, together with the fibrous Q-phase (e.g. 100–150 nm width and 300–500 nm length) growing along the  $\theta$ - $Al_2Cu$  phase and few 150–200 nm Si particles trapped between Q and  $\theta$ - $Al_2Cu$  phases, as shown in Fig. 4a–c and confirmed by SADPs (Fig. 4d) corresponded to  $\alpha$ -Al  $\langle 100 \rangle$ , Si  $\langle 001 \rangle$ , Q  $\langle 1\ 1\ \bar{2}\ 9 \rangle$  and  $\theta$ - $Al_2Cu$   $\langle 110 \rangle$ , respectively. However, such four-phase microstructure changed to a mixture of equiaxed  $\alpha$ -Al,

**Table 2**  
A list of multicomponent alloys studied.

Number of components	Alloy composition (at.%)
5	Al <sub>77</sub> Cu <sub>13</sub> Si <sub>6</sub> Mg <sub>3</sub> Ni <sub>1</sub>
11	Al <sub>70.5</sub> Cu <sub>18</sub> Si <sub>0.9</sub> Mg <sub>6</sub> Ca <sub>0.9</sub> Fe <sub>0.2</sub> Mn <sub>0.5</sub> Ni <sub>0.8</sub> Ti <sub>0.5</sub> Zr <sub>0.1</sub> Zn <sub>1.6</sub>
13	Al <sub>72</sub> Cu <sub>17</sub> Si <sub>0.9</sub> Mg <sub>3.8</sub> Ca <sub>0.7</sub> Fe <sub>0.2</sub> Mn <sub>0.7</sub> Ni <sub>0.9</sub> Ti <sub>0.4</sub> Zr <sub>0.1</sub> Ag <sub>1.6</sub> Sn <sub>0.7</sub> Zn <sub>1</sub>

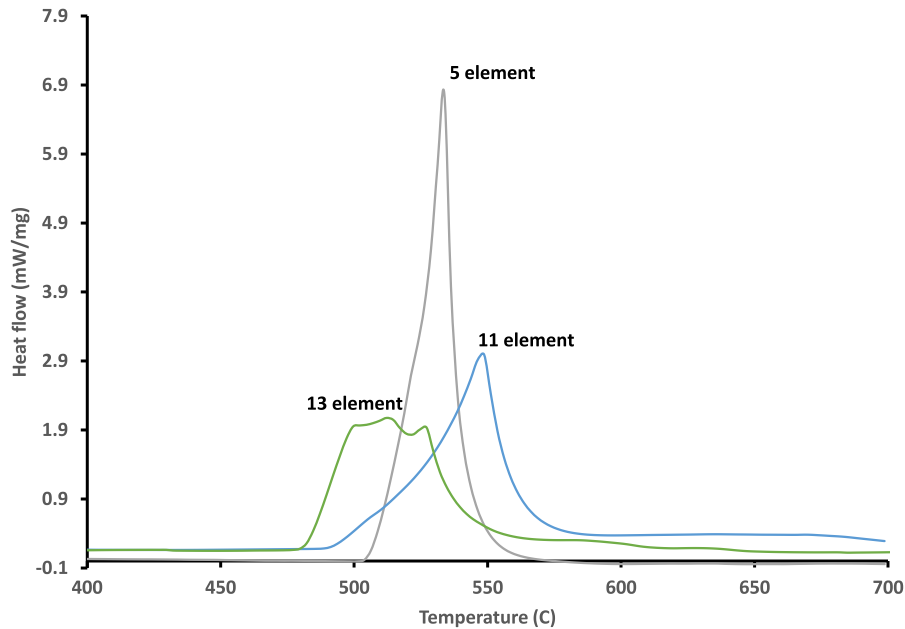

**Fig. 6.** DSC traces of 5-, 11- and 13-element multicomponent alloys obtained from heating at a rate of 20 K/min.

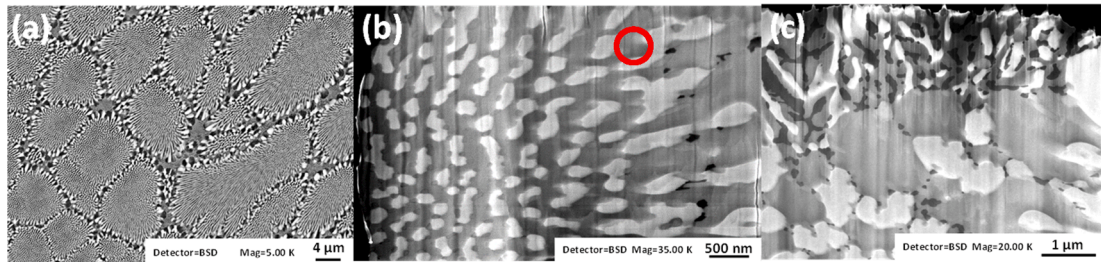

**Fig. 7.** SEM micrograph of cellular eutectic microstructure in suction cast quinary Al<sub>77</sub>Cu<sub>13</sub>Si<sub>6</sub>Mg<sub>3</sub>Ni<sub>1</sub> alloy (a), together with FIB-SEM micrographs of the cell (b) and cellular boundary (c) regions taken using the in-lens detector.

$\theta$ -Al<sub>2</sub>Cu and Si phases, together with platelets of Q phase, as shown in Fig. 4c. The sizes of Si,  $\theta$ -Al<sub>2</sub>Cu and Q phases reduced to 40–90 nm, 50–100 nm and 100 nm width by 100–250 nm length, respectively.

The orientation relationship (OR) of eutectic  $\theta$ -Al<sub>2</sub>Cu,  $\alpha$ -Al and Q phases in the cellular region exhibited the following orientation relationship as determined by T-EBSD technique (Fig. 5):

$$\{211\}_{\theta\text{-Al}_2\text{Cu}} // \{111\}_{\text{Al}} // \{31\bar{4}0\}_Q \text{ and } \langle 120 \rangle_{\theta\text{-Al}_2\text{Cu}} // \langle 110 \rangle_{\text{Al}} // \langle 0001 \rangle_Q$$

The  $\alpha$ -Al/ $\theta$ -Al<sub>2</sub>Cu eutectic phases in quaternary alloy retained a similar OR to that reported in binary Al-Cu system [9]. Hence in the ( $\alpha$ -Al +  $\theta$ -Al<sub>2</sub>Cu + Q-phase + Si) quaternary eutectic, Si faceted phase grows independently, while  $\alpha$ -Al,  $\theta$ -Al<sub>2</sub>Cu and Q-phase grow cooperatively, maintaining the OR.

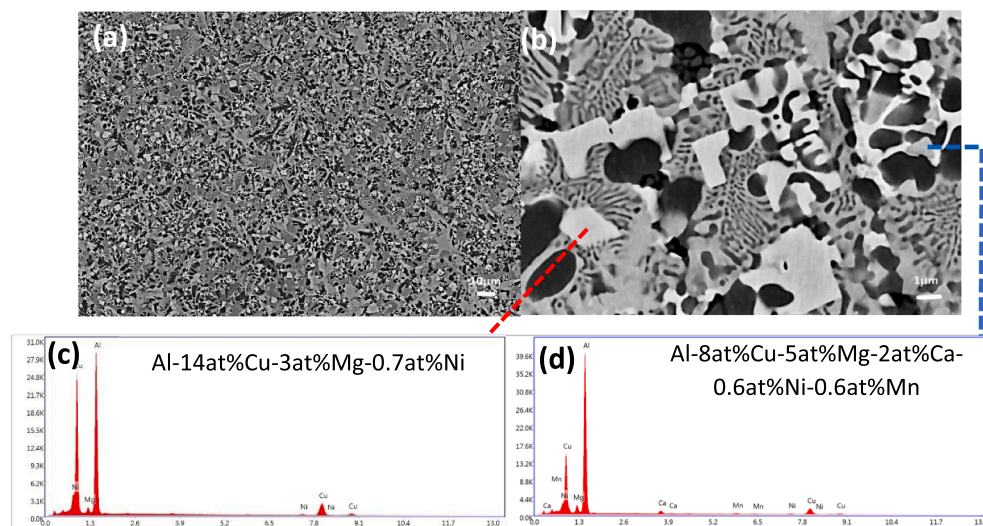


Fig. 8. BSE-SEM micrographs of 11-element multicomponent alloy taken at low magnification (a) and high magnification (b) together with EDX spectra of white (c) and grey (d) regions.

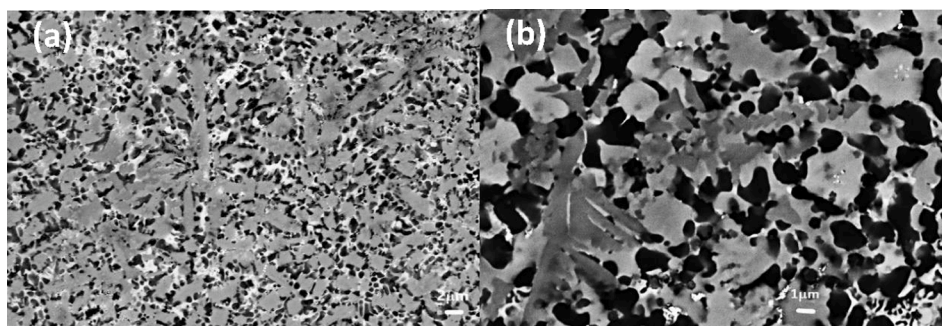



Fig. 9. BSE-SEM micrographs of 13-element multicomponent alloy taken as low magnification (a) and high magnification (b).

## 5. Multicomponent eutectic alloys beyond quaternary Al-Cu-Si-Mg system

Table 2 shows a list of multicomponent alloys prepared by suction casting and characterised in this study. Fig. 6 shows DSC traces of these multicomponent alloys subjected to a 20 K/min heating cycle. The 5-element multicomponent alloy consisted of a single endothermic peak, corresponding to the eutectic reaction. However, the DSC traces of 11-element and 13-element alloys consisted of multiple endothermic peaks overlapping each other. In all cases, solidification of primary phase from the melt has not been observed by DSC studies. However, the heat of fusion (i.e. area under the peak) of 5-element multicomponent alloy is 337 J/g, which is higher than 257 J/g in 11-element and 272 J/g in 13-element alloys. This is contributed to the lower onset melting temperature of 11- and 13-element multicomponent alloys as compared to 5-element multicomponent alloy.

Fig. 7a shows typical as-solidified microstructure of suction cast  $\text{Al}_{77}\text{Cu}_{13}\text{Si}_6\text{Mg}_3\text{Ni}_1$  quinary alloy. It has a similar cellular eutectic microstructure (Fig. 7b) with ultrafine eutectic mixture at the intercellular region (Fig. 7c) as compared to that found in  $\text{Al}_{76}\text{Cu}_{14}\text{Si}_7\text{Mg}_3$  quaternary alloy. From the SEM micrographs, a four-phase eutectic microstructure was observed and it consisted of  $\alpha$ -Al (light grey),  $\theta$ - $\text{Al}_2\text{Cu}$  (white), Q-phase (dark grey) as marked by a red circle in Fig. 7b and Si (black). The Q-phase is formed on the  $\theta$ - $\text{Al}_2\text{Cu}$  lamella. According to calphad calculation from Thermocalc, this quinary alloy comprises of five phases at various proportion at room temperature. They are  $\alpha$ -Al (51 vol%);  $\theta$ - $\text{Al}_2\text{Cu}$  (34 vol%); Q-phase (9.5 vol%); Si (4 vol%); and  $\text{Al}_3\text{Ni}$  (2 vol%). The absence of  $\text{Al}_3\text{Ni}$  phase in the microstructure of this alloy from the SEM studies can be attributed to a combination of low volume fraction and its similar contrast to  $\theta$ - $\text{Al}_2\text{Cu}$  phase. The coarsening of eutectic lamellae was also observed at the cell boundary. In addition, the proportions of these eutectic phases within the intercellular region are different from those within the cellular region due to solute redistribution and enrichment at the liquid/solid interface.

As the number of elements increased from 5 to 11, the as-solidified microstructure of  $\text{Al}_{70.5}\text{Cu}_{18}\text{Si}_{0.9}\text{Mg}_6\text{Ca}_{0.9}\text{Fe}_{0.2}\text{Mn}_{0.5}\text{Ni}_{0.8}\text{Ti}_{0.5}\text{Zr}_{0.1}\text{Zn}_{1.6}$  became complex, as shown in Fig. 8 and deviated from those in binary, ternary, quaternary and quinary eutectic alloys. The microstructure of the 11-element multicomponent alloy consisted of small blocky intermetallic (white),  $\alpha$ -Al (black) and coarse intermetallic compound (grey) phases, as shown in Fig. 8a. At high magnification, lamellar eutectic mixture (black + grey) was found

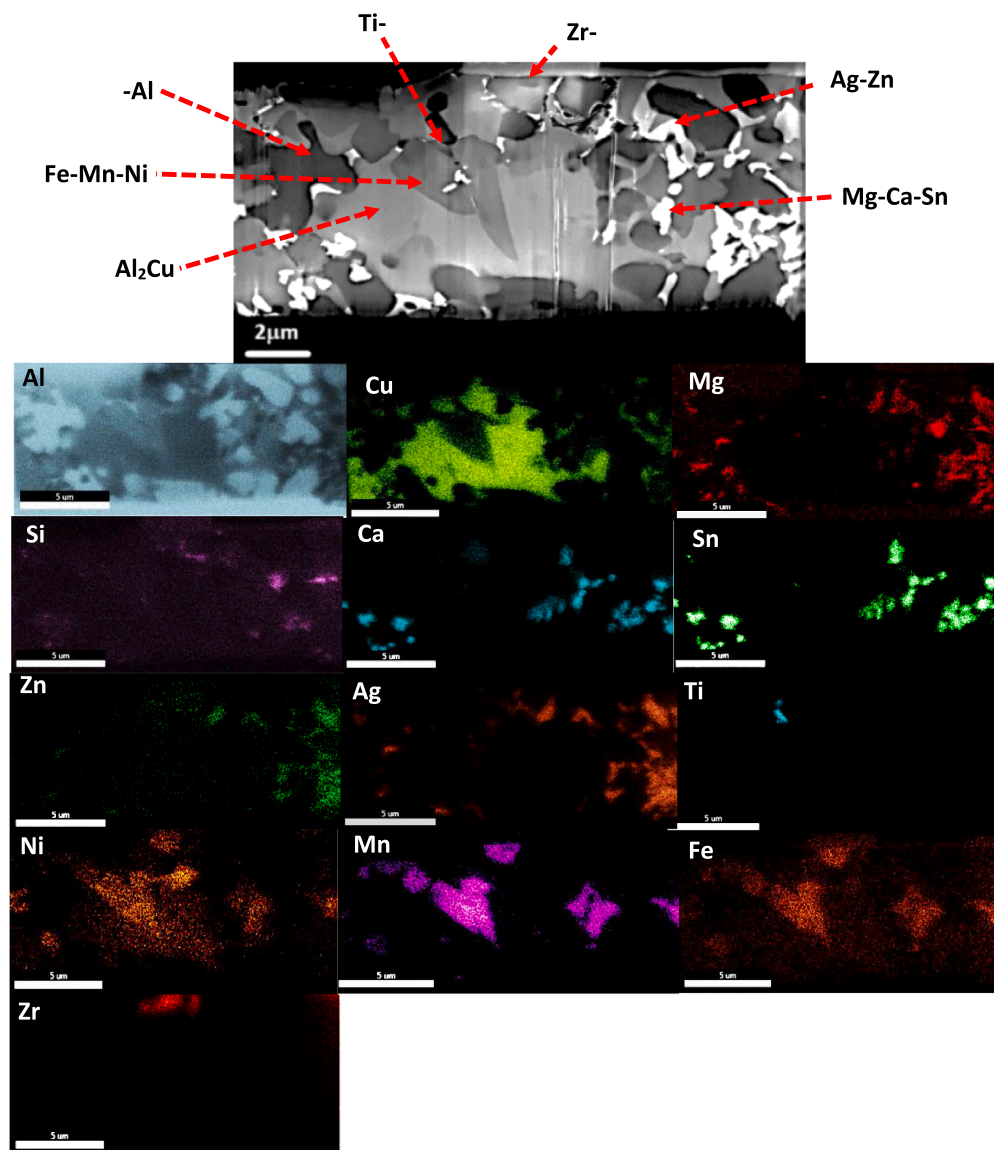

**Fig. 10.** FIB-SEM micrograph of  $\text{Al}_{72}\text{Cu}_{17}\text{Si}_{0.9}\text{Mg}_{3.8}\text{Ca}_{0.7}\text{Fe}_{0.2}\text{Mn}_{0.7}\text{Ni}_{0.9}\text{Ti}_{0.4}\text{Zr}_{0.1}\text{Ag}_{1.6}\text{Sn}_{0.7}\text{Zn}_1$  alloy, together with X-ray maps showing the corresponding element within each phase.

together with blocky phase (white), as shown in Fig. 8b. The composition of blocky phase (white) was determined as Al-14at%Cu-3at%Mg-0.7at%Ni from EDX spectrum (Fig. 8c). This is similar to T-phase ( $\text{Al}_6\text{MgCu}$ ) intermetallic compound but with the incorporation of a minor amount Ni, giving  $\text{Al}_6(\text{MgCuNi})$ . However, the grey phase is an unknown compound but has a composition of Al-8 at%Cu-5at%Mg-2at%Ca-0.6%Ni-0.6at%Mn compound, as shown in EDX spectrum (Fig. 8d). The ratio of Al/Cu in this complex unknown compound is similar to  $\text{Cu}_2\text{Mn}_3\text{Al}_{20}$  intermetallic compound but with a lower concentration of Mn, giving  $\text{Cu}_2(\text{MnMgCaNi})_3\text{Al}_{20}$ . The lamellar eutectic region consisted of  $\alpha\text{-Al}$  and Al-8at%Cu-5at%Mg-2at%Ca-0.6%Ni-0.6at%Mn multicomponent compound based on the contrast of the phase in the BSE-SEM micrograph, as shown in Fig. 8b. The solidification of this 11-element multicomponent alloy may involve two stages: (a) formation of coarse phase mixture (e.g.  $\alpha\text{-Al}$ ,  $\text{Al}_6(\text{MgCuNi})$ ,  $\text{Al}_{20}\text{Cu}_2(\text{MgCaNiMn})_3$ ) at high temperature; and (b) a fine lamellar eutectic mixture (e.g.  $\alpha\text{-Al}$ ,  $\text{Al}_6(\text{MgCuNi})$ ) at low temperature. This is reflected by asymmetry of DSC melting peak of 11-element multicomponent alloy as shown in Fig. 6.

In 13-element multicomponent alloy ( $\text{Al}_{72}\text{Cu}_{17}\text{Si}_{0.9}\text{Mg}_{3.8}\text{Ca}_{0.7}\text{Fe}_{0.2}\text{Mn}_{0.7}\text{Ni}_{0.9}\text{Ti}_{0.4}\text{Zr}_{0.1}\text{Ag}_{1.6}\text{Sn}_{0.7}\text{Zn}_1$ ), the as-solidified microstructure consisted of three phases corresponding to grey, black and white regions, as shown in the BSE-SEM micrograph taken at a low magnification (Fig. 9a). However, at high magnification (Fig. 9b), it revealed a complex microstructure comprised of three interconnected phases corresponding to black, light and dark grey regions, together pockets of fine two-phase lamellar morphology, corresponding to white and dark regions. However, X-ray maps obtained from the FIB-SEM specimen showed a very complex



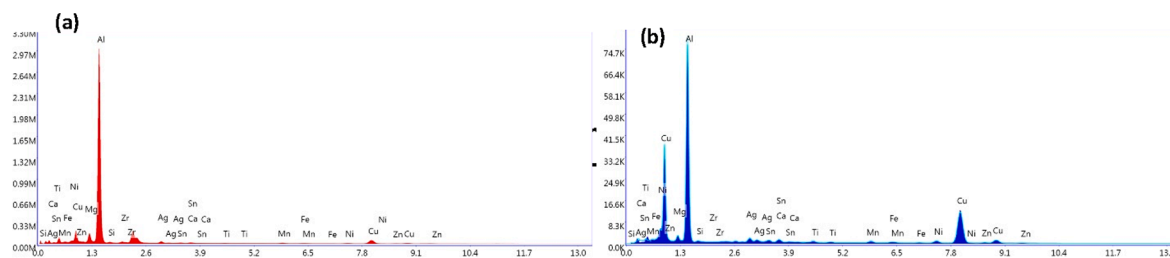


Fig. 11. EDX spectra of Al-rich (a) and Cu-containing phases in  $\text{Al}_{72}\text{Cu}_{17}\text{Si}_{0.9}\text{Mg}_{3.8}\text{Ca}_{0.7}\text{Fe}_{0.2}\text{Mn}_{0.7}\text{Ni}_{0.9}\text{Ti}_{0.4}\text{Zr}_{0.1}\text{Ag}_{1.6}\text{Sn}_{0.7}\text{Zn}_1$  alloy.

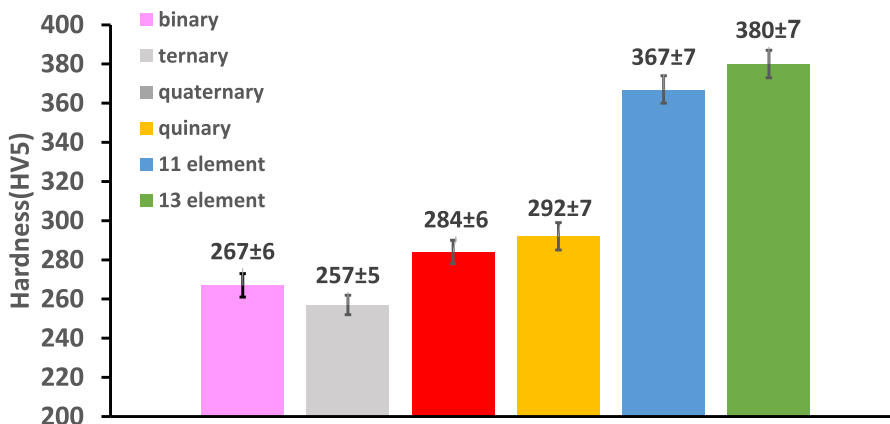


Fig. 12. A plot of average Vickers Hardness of suction cast alloys from binary to 13-element multicomponent systems.

microstructure, consisting of seven phases including Al-, Cu-, Zr-, Ti-, Si, Ag-Zn, Mg-Ca-Sn, Ni-Fe-Mn, as shown in Fig. 10. The Al-rich and Cu-containing phases corresponded to  $\alpha$ -Al and  $\text{Al}_2\text{Cu}$  phases with compositions of Al-5.6at%Cu-5.4at%Mg-1.2at%Si-0.3at%Ca-0.4at%Ni-0.7at%Zr-0.5at%Mn-0.2at%Fe-0.2at%Ti-0.3at%Ag-0.3at%Sn-0.2at%Zn (Fig. 11a) and Al-33at%Cu-2.3at%Mg-0.3at%Si-0.7at%Ca-1.8at%Ni-1at%Mn-0.6at%Fe-0.7at%-0.9at%Ag-0.6at%Sn-0.9at%Zn (Fig. 11b), respectively. There are four Ag-Zn intermetallic compounds [70] and one ternary Mg-Ca-Zn intermetallic compound [71]. Ternary Fe-Mn-Ni phase can exist as solid solution if the composition is located near the Fe corner of the ternary alloy system [72], while Zr- and Ti- containing phases are unknown and yet to be identified. The formation of these phases involves three stages as illustrated by the three overlapping DSC melting peaks in Fig. 6. The solidification behaviour of such alloy is very complex and further studies are being carried out to understand their microstructural evolution.

## 6. Hardness of binary eutectic to multicomponent alloys

The combination of refined microstructure and presence of Q-phase has led to the moderate increase in average hardness from 267HV in  $\text{Al}_{84}\text{Cu}_{16}$  to 292HV in  $\text{Al}_{77}\text{Cu}_{13}\text{Si}_6\text{Mg}_3\text{Ni}_1$ , as shown in Fig. 12. However, 11- and 13-elements multicomponent alloys exhibited average hardness values of 367HV and 380HV, respectively. Such significant increase in hardness is contributed by a complex microstructure of multiple phases including solid solutions and intermetallic compounds.

## 7. Conclusions

This review article has shown our strong understanding and knowledge of eutectic alloys in the low order constituent binary and ternary systems. When the alloy systems become more complex and are based on a large number of constituents, our knowledge of eutectic solidification is limited and it is restricted mainly to two-phase eutectic microstructure. This is partly due to the difficulty of finding eutectic compositions in high order constituent alloy systems without any prior knowledge of co-existed eutectic phases. Our recent attempt to search for eutectic compositions in alloy systems beyond five constituents have led to the following conclusions:

- The melting temperature and latent heat of fusion decreased with increasing number of components in the alloy system.
- Ternary, quaternary and quinary eutectic alloys exhibited a similar microstructure of cellular colonies of lamellar morphology with ultrafine intercellular eutectic mixture.
- The as-solidified microstructure of 11- and 13-element multicomponent alloys comprised of multiple (e.g. 3–7) phases including solid solutions and intermetallic compounds.

- The average hardness increased with increasing number of components in the alloy systems.

This work has identified the knowledge gap of eutectic point(s) within the large composition space of high order multicomponent alloys. The newly studied multicomponent alloys offer superior hardness due to their complex multiphase microstructure. Finally, this opens up a novel approach to designing high strength aluminium based multicomponent alloys.

### Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

### Acknowledgement

The authors would like to thank Engineering and Physical Sciences Research Council (EPSRC) for the financial support on Future Liquid Metal Engineering (LiME) Hub (Grant No. EP/N007638/1) at BCAST, where this work was carried out. We are grateful to Dr. Vivian Tong at National Physical Laboratory for the technical support on T-EBSD studies. We would also like to thank Professor Z. Fan for the provision of processing and characterisation facilities at BCAST and the fruitful discussion on multicomponent eutectic alloys. Qing Cai is very grateful to Brunel University London for the financial support on his PhD studies. Finally, we would like to thank the Experimental Technique Centre(ETC) at Brunel University London for the provision of the electron microscopy characterisation facilities.

### References

- [1] Guthrie F. To cite this article: Frederick Guthrie (1884) LII. On  $\delta$ -eutectia, The London, Edinburgh, and Dublin Philosophical Magazine and. J Sci 2010;17: 462–482.
- [2] Fisher DJ, Kurz W. A theory of branching limited growth of irregular eutectics. Acta Metall 1980;28:777–94.
- [3] Huang W, Wang L. Solidification researches using transparent model materials - a review. Sci China Technol Sci 2012;55:377–86.
- [4] Orea VM, Peña JI, Oliete PB, Merino RI, Larrea A. Growth of eutectic ceramic structures by directional solidification methods. J Cryst Growth 2012;360: 99–104.
- [5] Jackson KA, Hunt JD. Lamellar and rod eutectic growth. Trans Metall Soc AIME 1966;236:1966–11129.
- [6] Hellawell A. The growth and structure of eutectics with silicon and germanium. Prog Mater Sci 1970;15:3–78.
- [7] Shamsuzzoha M, Hogan LM. Crystal morphology of unmodified aluminium-silicon eutectic microstructures. J Cryst Growth 1986;76:429–39.
- [8] Risueño E, et al. Mg-Zn-Al eutectic alloys as phase change material for latent heat thermal energy storage. Energy Proc 2015;69:1006–13.
- [9] Cantor B, Chadwick GA. The growth crystallography of unidirectionally solidified Al-Al3Ni and Al-Al2Cu eutectics. J Cryst Growth 1974;23:12–20.
- [10] Cantor B, Chadwick GA. The tensile deformation of unidirectionally solidified Al-Al3Ni and Al-Al2Cu eutectics. J Mater Sci 1975;10:578–88.
- [11] Hecht U, Witusiewicz V, Drevermann A, Rex S. Formation of eutectic cells in ternary Al-Cu-Ag alloys. Solidif Cryst 2005;259–70. <https://doi.org/10.1002/3527603506.ch28>.
- [12] Manjura Hoque S, Mäkinen SK, Pal A, Ayyub P, Chattopadhyay K. Structural and magnetic properties of ultra-small scale eutectic CoFeZr alloys. J Alloys Compd 2015;620:442–50.
- [13] Yang C, Zhang J, Huang H, Song Q, Liu F. Stability of metastable phase and soft magnetic properties of bulk Fe-B nano-eutectic alloy prepared by undercooling solidification combined with CU-mold chilling. Phys B Condens Matter 2015;476:132–6.
- [14] Park JM, et al. Nanostructure-dendrite composites in the Fe-Zr binary alloy system exhibiting high strength and plasticity. Scr Mater 2007;57:1153–6.
- [15] Gogebakan M, Kursun C, Gunduz KO, Tarakci M, Gencer Y. Microstructural and mechanical properties of binary Ni-Si eutectic alloys. J Alloys Compd 2015;643: S219–25.
- [16] Louzguine DV, Kato H, Louzguina LV, Inoue A. High-strength binary Ti-Fe bulk alloys with enhanced ductility. J Mater Res 2004;19:3600–6.
- [17] Campbell FC. Ch 5. Eutectic Alloy Systems; 2012. p. 87–116.
- [18] Chanda B, Potnis G, Jana PP, Das J. A review on nano-/ultrafine advanced eutectic alloys. J Alloys Compd 2020;827:154226.
- [19] Ruan Y, Wei BB. Rapid solidification of undercooled Al-Cu-Si eutectic alloys. Chinese Sci Bull 2009;54:53–8.
- [20] Zhai W, Lu X, Wei B. Microstructural evolution of ternary Ag33Cu42Ge25 eutectic alloy inside ultrasonic field. Prog Nat Sci Mater Int 2014;24:642–8.
- [21] Park EM, et al. Solid-state phase transformation-induced heterogeneous duplex structure in Ti-Sn-Fe alloys. J Alloys Compd 2012;515:86–9.
- [22] Das J, Kim KB, Baier F, Löser W, Eckert J. High-strength Ti-base ultrafine eutectic with enhanced ductility. Appl Phys Lett 2005;87:1–3.
- [23] Park JM, Kim DH, Kim KB, Eckert J. Improving the plasticity of a high strength Fe-Si-Ti ultrafine composite by introduction of an immiscible element. Appl Phys Lett 2010;97:2008–11.
- [24] Park JM, Kima DH, Kim KB, Mattern N, Eckert J. Evolution of constitution, structure, and mechanical properties in Fe-Ti-Zr-B heterogeneous multiphase composites. J Mater Res 2011;26:365–71.
- [25] Baker I, Wu M, Wang Z. Eutectic/eutectoid multi-principle component alloys: a review. Mater Charact 2019;147:545–57.
- [26] He F, et al. Grouping strategy in eutectic multi-principal-component alloys. Mater Chem Phys 2019;221:138–43.
- [27] Jin X, Zhou Y, Zhang L, Du X, Li B. A new pseudo binary strategy to design eutectic high entropy alloys using mixing enthalpy and valence electron concentration. Mater Des 2018;143:49–55.
- [28] Lu Y, et al. Directly cast bulk eutectic and near-eutectic high entropy alloys with balanced strength and ductility in a wide temperature range. Acta Mater 2017; 124:143–50.
- [29] Rogal L, Morgiel J, Świątek Z, Czerwiński F. Microstructure and mechanical properties of the new Nb25Sc25Ti25Zr25 eutectic high entropy alloy. Mater Sci Eng A 2016;651:590–7.
- [30] Jin X, et al. A new CrFeNi2Al eutectic high entropy alloy system with excellent mechanical properties. J Alloys Compd 2019;770:655–61.
- [31] Dong Y, Lu Y, Kong J, Zhang J, Li T. Microstructure and mechanical properties of multi-component AlCrFeNiMo x high-entropy alloys. J Alloys Compd 2013; 573:96–101.
- [32] Guo Y, et al. A superfine eutectic microstructure and the mechanical properties of CoCrFeNiMox high-entropy alloys. J Mater Res 2018;33:3258–65.
- [33] Jiang L, et al. Effect of Mo and Ni elements on microstructure evolution and mechanical properties of the CoFeNiVMoy high entropy alloys. J Alloys Compd 2015;649:585–90.
- [34] Jiang L, et al. Effects of Nb addition on structural evolution and properties of the CoFeNi2V0.5 high-entropy alloy. Appl Phys A Mater Sci Process 2015;119: 291–7.
- [35] Vrtnik S, et al. Magnetism of CoCrFeNiZrx eutectic high-entropy alloys. Intermetallics 2018;93:122–33.

- [36] Jiang H, et al. Microstructures and mechanical properties of Co<sub>2</sub>MoxNi<sub>2</sub>VWx eutectic high entropy alloys. *Mater Des* 2016;109:539–46.
- [37] Lu Y, et al. A new strategy to design eutectic high-entropy alloys using mixing enthalpy. *Intermetallics* 2017;91:124–8.
- [38] Baker I, Meng F, Wu M, Brandenberg A. Recrystallization of a novel two-phase FeNiMnAlCr high entropy alloy. *J Alloys Compd* 2016;656:458–64.
- [39] Tan Y, Li J, Wang J, Kou H. Seaweed eutectic-dendritic solidification pattern in a CoCrFeNiMnPd eutectic high-entropy alloy. *Intermetallics* 2017;85:74–9.
- [40] Ma SG, Zhang Y. Effect of Nb addition on the microstructure and properties of AlCoCrFeNi high-entropy alloy. *Mater Sci Eng A* 2012;532:480–6.
- [41] Park JM, et al. High-strength bulk Al-based bimodal ultrafine eutectic composite with enhanced plasticity. *J Mater Res* 2009;24:2605–9.
- [42] Morando C, Garbellini O, Fornaro O, Palacio H. Morphology and phase formation during the solidification of alcuSi ternary eutectic system. In: 65th ABM Int. Congr. 18th IFHTSE Congr. 1st TMS/ABM Int. Mater. Congr. 2010, vol. 6; 2010. p. 4610–7.
- [43] Mccartney DG, Jordan RM, Hunt JD. The Structures Expected in a Simple Ternary Eutectic System: Part II. The Al-Ag-Cu Ternary System.
- [44] Semenova EL. Aluminium – Magnesium – Nickel; 1991. p. 150–6.
- [45] Rios CT, Milenkovic S, Gama S, Caram R. Influence of the growth rate on the microstructure of a Nb-Al-Ni ternary eutectic. *J Cryst Growth* 2002;237–239:90–4.
- [46] Contieri RJ, Rios CT, Zanotello M, Caram R. Growth and three-dimensional analysis of a Nb-Al-Ni ternary eutectic. *Mater Charact* 2008;59:693–9.
- [47] Tiwary CS, Kashyap S, Chattopadhyay K. Development of alloys with high strength at elevated temperatures by tuning the bimodal microstructure in the Al-Cu-Ni eutectic system. *Scr Mater* 2014;93:20–3.
- [48] Lu XY, Wang WL, Zhai W. Ternary eutectic and peritectic solidification of undercooled liquid Fe-Mo-Si alloys. *Mater Charact* 2015;110:252–7.
- [49] Huang H, Yang C, Song Q, Ye K, Liu F. Nano-eutectic structure formation and soft magnetic properties of bulk ternary Fe-B-M (M = Si, Cu) alloys. *J Appl Phys* 2016;120.
- [50] Kaygisiz Y, Marasli N. Directional solidification of Al-Cu-Si-Mg quaternary eutectic alloy. *J Alloys Compd* 2017;721:764–71.
- [51] Stockdale D. Numerical relationships in binary metallic systems. *Proc R Soc London Ser A - Math Phys Sci* 1935;152:81–104.
- [52] Hume-Rothery W, Anderson E. Eutectic compositions and liquid immiscibility in certain binary alloys. *Philos Mag* 1960;5:383.
- [53] Frank FC. Supercooling of liquids. *Proc Roy Soc London, Ser A, Math Phys Sci* 1952;215:43–6.
- [54] Ma YP, et al. Composition formulas of binary eutectics. *Sci Rep* 2015;5:1–16.
- [55] Binary Alloy Phase Diagrams, 2nd edition. ASM International; 1990.
- [56] Handbook of Ternary Alloy Phase Diagrams. 3. ASM International; 1995.
- [57] Ivashchenko AV, Titov VV, Kovshev EI. Liquid crystalline compounds - 3. On Applicability of Schroeder - Van Laar equations to liquid crystals mixtures. *Mol Cryst Liq Cryst* 1976;33:195–200.
- [58] Mamedov AN, Mekhdiev IG. Prediction of the quaternary eutectic. *Thermochim Acta* 1995;269–270:73–8.
- [59] Ivashchenko AV, Titov VV, Kovshev EI. Molecular crystals and liquid crystals liquid crystalline compounds: III On Applicability of Schröder-Van Laar equations to liquid crystals mixtures. *Mol Cryst Liq Cryst* 1976;33:195–200.
- [60] Ding ZY, He QF, Yang Y. Exploring the design of eutectic or near-eutectic multicomponent alloys: from binary to high entropy alloys. *Sci China Technol Sci* 2018;61:159–67.
- [61] Lutsyk VI, Zelenaya AE, Savinov VV, Sumkina OG, Savinov VV. Precision of the eutectic points determination by the isopleths. *IOP Conf Ser: Mater Sci Eng* 2011; 18:162021. <https://doi.org/10.1088/1757-899X/18/16/162021>.
- [62] Raud R, Jacob R, Bruno F, Will G, Steinberg TA. A critical review of eutectic salt property prediction for latent heat energy storage systems. *Renew Sustain Energy Rev* 2017;70:936–44.
- [63] Farkas DBC. New eutectic alloys and their heats of transformation. *Metall Mater Trans A* 1985;16A:323.
- [64] Zhang C, Zhang F, Chen S, Cao W. Computational thermodynamics aided high-entropy alloy design. *JOM* 2012;64:839.
- [65] Hsu C-Y, et al. Phase diagrams of high-entropy alloy system Al-Co-Cr-Fe-Mo-Ni. *JoM* 2013;65:1829.
- [66] Zhang F, et al. An understanding of high entropy alloys from phase diagram calculations. *Calphad Comput Coupling Phase Diagrams Thermochem* 2014;45: 1–10.
- [67] Zhang C, et al. Understanding phase stability of Al-Co-Cr-Fe-Ni high entropy alloys. *Mater Des* 2016;109:425–33.
- [68] Zhao J, Yuan Y, Cui Fu. Relationship between the Cu content and thermal properties of Al-Cu alloys for latent heat energy storage; 2017. <https://doi.org/10.1007/s10973-017-6153-3>.
- [69] Srivastava RM, Eckert J, Löser W, Dhindaw BK, Schultz L. Cooling rate evaluation for bulk amorphous alloys from eutectic microstructures in casting processes. *Mater Trans* 2002;43.
- [70] Palenzona A, Manfrinetti P, Fornasini ML. Phase diagram of the Ca-Sn system. *J Alloys Compd* 2000;312:165–71.
- [71] Hort N, Huang YD, Leil TA, Rao KP, Kainer KU. Properties and processing of magnesium-tin-calcium alloys. *Kov Mater* 2011;49:163–77.
- [72] Pustov LY, et al. Structure and phase transformations in Fe-Ni-Mn alloys nanostructured by mechanical alloying. *J Alloys Compd* 2009;483:200–3.